

Nigerian Journal

Of

Materials Science and Engineering (NJMSE)

Volumes 11 Issue 2

ISSN 214-453-2

December 2021

Materials Science & Technology Society of Nigeria (MSN)



An International Journal of the Materials Science and Technology Society of Nigeria

Nigerian Journal of Materials Science and Engineering (NJMSE)

Materials Science & Technology Society of Nigeria (MSN)

Copyright © 2021. Materials Science and Technology Society of Nigeria (MSN)

Volume 11 Issue 2, December 2021
ISSN 214-453-2

All Rights Reserved

Published by

Materials Science and Technology Society of Nigeria (MSN)
National Headquarters
Raw Materials Research and development Council (RMRDC) Laboratory Complex
Km. 10, Airport Road, Galadimawa,
Abuja. FCT. Nigeria
Tel.: +234-803-471-8487; +234-803-703-3052; +234-806-220-7420

<http://njmse.msn.ng/>

Emails: njmse@msn.ng; njmse.msn@gmail.com; njmsemanagingeditor@msn.ng;
editorinchief@msn.ng; njmse.editor.in.chief@gmail.com;

(NJMSE - An International Journal of the Materials Science and Technology Society of Nigeria)

Copyright© 2021. Nigerian Journal of Materials Science and Engineering (NJMSE).

NJMSE Editorial Board

Management Team

Dr. **Babatope** Babaniyi; Obafemi Awolowo University, Ile-Ife. Nigeria. **Editor-in-Chief.**

Prof. **Giwa** Abdulraheem; Ahmadu Bello University, Zaria. Nigeria. **Managing Editor.**

Dr. (Engr.) **Oyelami** Adekunle T., Federal University of Agriculture, Abeokuta, Nigeria.

Assistant Managing Editor

Engr. **Ogunkoya** Olatunji; Engineering Materials Development Institute. Akure. Nigeria.

Editorial Desk / Processing Officer.

Dr. **Edema** O. Gregory, Federal Polytechnic Auchi, Nigeria. **Assistant Processing Officer.**

Associate Editors

Prof. Ishiaku U. S.; Ahmadu Bello University, Zaria. Nigeria

Prof. Tunde Ojumu; Cape Peninsula University of Technology, South Africa.

Prof. Eleruja Marcus Adebola; Obafemi Awolowo University, Ile-Ife. Nigeria

Dr. Umar Ahmadu; Federal University of Technology, Minna. Nigeria

Dr. Ahmed Tajudeen; Federal University Lokoja. Nigeria

Prof. Idenyi Ede Ndubuisi; Ebonyi State University, Abakaliki. Nigeria

Dr. Ajayi Olusegun; Ahmadu Bello University, Zaria. Nigeria

Dr. Adetunji Adelana R.; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Baba Alafara; University of Ilorin, Ilorin. Nigeria

Prof. Hassan S. Bolaji; University of Lagos, Lagos. Nigeria

Prof. Nwoye Chukwuka I.; Nnamdi Azikiwe University, Awka. Nigeria

Dr. Oyatogun Grace Modupe; Obafemi Awolowo University, Ile-Ife. Nigeria

Dr. Otemuyiwa I.O; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Ikhuoria Esther; University of Benin. Nigeria

Dr. Oluwajobi Akinjide Olajide, Obafemi Awolowo University. Nigeria.

Dr. Odusanya A. Sola; Sheda Sci. and Technology Complex, Abuja Nigeria

Prof. Borode Joseph Olatunde; Federal University of Technology, Akure. Nigeria

Dr. Odo Dele; Federal University, Oye. Nigeria

Prof. Adewuyi Benjamin; Federal University of Technology, Akure. Nigeria

Dr. Adekunle A. Saheed.; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Esezobor David; University of Lagos. Lagos. Nigeria

Prof. Dare E. Olugbenga; Federal University of Agriculture, Abeokuta. Nigeria

Prof. Boyo Adenike; Lagos State University, Lagos. Nigeria.

Prof. Dauda Mohammed; University of Maiduguri, Maiduguri, Nigeria.

Editorial Advisory Board

Prof. Soboyejo Winston Wole; Worcester Polytechnic Institute, Worcester. USA

Prof. Salvastano Holmer, Jnr. University of Sao Paulo, Sao Paulo, Brazil

Prof. Thomas Sabu; Mahatma Gandhi University, India

Prof. Sadiku Rotimi; Tshwane University of Technology, Pretoria. South Africa

Prof. Ghosh Malay Kumar; CSIR-IMMT, Bhubanaswar. India

Prof. Olorunnisola Abel Olajide; University of Ibadan, Ibadan. Nigeria

Prof. Ahmed A. Salawu; Ahmadu Bello University, Zaria. Nigeria

Prof. Nkeonye Peter O.; Ahmadu Bello University, Zaria. Nigeria

Prof. Pelemo David A.; Obafemi Awolowo University, Ile-Ife. Nigeria

Prof. Onwualu Peter Azikiwe; University of Nigeria, Nsukka. Nigeria

Engr. Ogundade Kunle; Petroorganico Ltd. Lagos. Nigeria

Prof. Akinola A. P.; Obafemi Awolowo University, Ile-Ife. Nigeria

Editorial Comment

It is a great pressure for the editorial board of the Nigerian Journal of Materials Science and Engineering (NJMSE) to present Volume 11 Number 2 of the journal for 2021 for the world materials research and development community.

The Materials Science and Technology Society of Nigeria (MSN), as a forefront professional learned body, has made the publication of this research journal to be of very high standard comparable to any in her class. Our major thrust is to disseminate materials science and engineering and allied research activities from Nigeria, Africa and the world over. We are slowly and gradually impacting on the research community work with this specialised journal from a reputable learned and professional body in Nigeria. We are not insisting on number but we very much believe, with the thoroughness of our approach to the review and assessment process, we are convinced that with our resolve to publish twice a year presently, the board is convinced that more researcher would take advantage of this.

As a journal whose policy is to maintain the standard best practices and in addition, to help young researchers to advance in the art and science of scientific findings dissemination. It is heart-warming that we can look back and be glad to see the society publishing the 11th volume. These volumes and the previous ones would be available for FREE downloading on our society website (www.msn.ng) through a link prior to the specialised journal website to be available soon after overcoming our present challenges. Arrangements are in advanced stages for the hosting of this journal by reputable international online submission system which is presently being worked on.

Volume 11 (2021) Number 2 consists of thirteen (13) high standard articles covering different specialised areas of materials research. It is our hope that this humble effort, presently by voluntary efforts of senior members of the Society, would have enriched the information base and complemented Materials Research efforts from around the world.

We appreciate all our reviewers and associate editors involved for their prompt action on the manuscripts and cooperation as we look forward to submission of manuscripts which can be forwarded as detailed below.

Babaniyi Babatope. (PhD,MBA,FMSN,FIMMM(UK))
Editor-in-Chief.
Department of Physics and Engineering Physics,
Advanced Nanostructured Materials and Devices Research Group
Obafemi Awolowo University, Ile-Ife. Nigeria.
editorinchief@msn.ng; njmse.editor.in.chief@gmail.com
bbabatop@oauife.edu.ng; niyibabatope@gmail.com;

Manuscripts can also be submitted to:

Managing Editors, NJMSE.
njmse.msn@gmail.com; njmse@msn.ng; njmsemanagingeditor@msn.ng

Editor-in-Chief
editorinchief@msn.ng; njmse.editor.in.chief@gmail.com; bbabatop@oauife.edu.ng.

Website:
<http://njmse.msn.ng/>

GUIDE TO AUTHORS

AIM: To improve the international exchange of scientific research in materials science and engineering.

INTRODUCTION

The Nigerian Journal of Materials Science and Engineering (NJMSE) publishes reviews, full-length papers, and short communications recording original research results on, or techniques for studying the relationship between structure, properties, and uses of materials. The subjects are seen from international and interdisciplinary perspectives covering areas including metals, ceramics, glasses, polymers, composite materials, fibers, electronic materials, alternative energy materials, nanostructured materials, nanocomposites, biological, biomedical materials, etc. The NJMSE is now firmly established as the leading source of primary communication for scientists investigating the structure and properties of all engineering materials in Nigeria, Africa and the Rest of the World.

UNIQUENESS OF THE JOURNAL

NJMSE is introduced to publish research findings on current topical issues of interest to both public and private sectors. The scope of the Journal focuses on experimental, empirical and theoretical research in Materials Science and Engineering. Findings from multidisciplinary research covering diverse areas of interest with potential impact on the public and private sectors of both the national and international communities will be priorities of the journal. Our major focus is the use of Materials Science and Engineering principles to solve basic problems peculiar to Africa and the developing world while contributing to knowledge on the global scale.

GUIDE FOR AUTHORS

NJMSE welcomes research papers covering original work that has good potential for practical application. Submission of a manuscript will be held to imply that the work being reported is original and that the result has not been published previously nor been under considerations for publication elsewhere.

MANUSCRIPT PREPARATION

The format of the typescript should be as follows:

The official language of the journal is English. When writing do not mix languages, use US English completely or use UK English completely. It is expected that before submission, the manuscript will have been thoroughly reviewed and written in simple clear expression. Manuscript should be typewritten with double-spacing and 2.54 cm or 1 inch margins on all sides. Manuscripts should be submitted in electronic form and e-mailed directly to the addresses below in MS-Word format, double spacing with graphics at the end. Manuscripts should be arranged in the following order: title page, abstract, introduction, materials and methods, results and discussion, conclusions, acknowledgements, references. The manuscripts should follow the format listed below.

Title: The title page should contain the title [concise but clear expression, written in bold, upper case], followed by the authors [surname first, block letters throughout], and followed by their institutional affiliations and the e-mail address of the corresponding author. In case of many authors, please use numbers to differential their affiliation.

Abstract: An abstract of not more than 350 words should be supplied immediately before the beginning of the paper (Graphical abstracts are also acceptable).

Introduction: This should contain a brief review of literature, clearly stated objectives and justification for the study.

Materials and Methods: This should contain materials preparation procedure and major measurement patterns. Sufficient information should be provided to perform repetition of the experimental work.

Results and Discussion: The result section should contain appropriate tables, figures/illustrations. These should be pertinent to the work and should clearly indicate the degree of reliability of results. Tables should be numbered consecutively, with a short descriptive title in upper case (block letters) on top of the table. They should contain no vertical lines and no lines to separate the rows except the heading and the end of the table. Figures, micrographs, or illustrations must be clearly captioned, the captions at the bottom of each figure. Figures may not be used to repeat the information already presented in tables or text or vice versa. Micrographs and illustrations are considered as figures and must be labeled as such.

Conclusions: These should summarize any important conclusions emerging from the work.

Acknowledgements: These should be presented at the end of text and before the references. Technical assistance and advice may be acknowledged. Acknowledgments of financial support can also be stated in this section.

References:

Citing: Reference in the text should be made by the author's last name and year of publication, e.g. (Abel, 2007); (Abel and Babcock, 2007); (Bowen *et al.*, 2007). Two papers by the same author in the same year should be distinguished by a suffix, (a, b, etc) e.g. (Madonna, 2006a); (Madonna, 2006b).

Listing: This should be in alphabetical order and should follow this format: Name(s) and initial(s) of author(s), (year of publication), exact title of paper (in quote), the title of periodical, Vol. (number): initial and final page numbers. Please note that only name cited in the text can be used.

Serial: Briant C. L. and Banerji S. K. (1981). 'Tempered Martensite Embrittlement and Intergranular Fracture in an Ultrahigh Strength Sulfur Doped Steel', *Metall. Trans. A*, 12A:309-319. (Please pay attention to punctuation).

Book: Samuels, L. E. (1982). *Metallographic Polishing by Mechanical Methods*, 3ed., American Society for Metals, Metals, Park, Ohio.

Proceeding: Olorunnisola A. O. (2006). The potentials of bamboo as novel building and furniture production materials in Nigeria, pp.180-185. In *Proc. Nigerian Materials Congress (NIMACON 2006)*, (B. Babatope and W. O. Siyanbola, Eds.), organized by Materials Society of Nigeria, 15-18 November 2006, Abuja, Nigeria.

Heading and sub-heading: All headings and sub-headings should be numbered and started from the left hand margin. All headings should be in upper case while sub-headings should be in lower case except the first letter.

Equations: Equations should be distinctly typed using Microsoft equation. Avoid powers of "e" and use "exp". Equations should be numbered consecutively by Arabic numerals in parenthesis at the right margin. In the text, such equation should be cited as Equation (1) etc.

Units and symbols: Symbols, units and nomenclature should conform to the recommendations of the International Union of Pure Applied Chemistry (IUPAC). SI units should be used for physical quantities.

Peer-Review: All submitted manuscripts are subjected to a peer- review process and galley proofs will be sent to the first or corresponding author where necessary.

SUBMISSION OF MANUSCRIPTS

A Processing Fee of N10,000.00 only is payable per article. All submitted articles MUST be accompanied with scanned Bank (detail below) Tellers or On-line transfer receipt as evidence of payment. Send your article(s) and Bank Teller to: njmsemanagingeditor@msn.ng; njmse@msn.ng; NJMSE.msn@gmail.com. All submission of manuscripts must be sent on-line to fast-track processing and simplify the refereeing process.

PAGE CHARGE

Corresponding Authors of accepted articles will be required to pay a sum of N10,000.00 only as processing fee (at the point of acknowledging receipt of manuscript) and N10,000.00 (non-members and non-financial members of MSN), N5,000.00 (financial members of MSN) after acceptance (or \$100.00 USD for processing and acceptance for other countries). They will receive free ecopy of the NJMSE volume in .pdf version. The ecopy is available online at <http://njmse.msn.ng> and can be downloaded free. However, printed copy(ies) may be requested for extra payment.

COPYRIGHT

Submission of an article for publication implies the transfer of the copyright of the manuscript from the author(s) to the publisher upon acceptance and that the manuscript has not been previously published elsewhere. This is the responsibility of the authors. Accepted papers become the permanent property of the publisher and may not be reproduced by any means without the written consent of the Editor-in-Chief.

Account Details: GTB PLC A/C No. 0171794514. Materials Science and Technology Society of Nigeria.

All Correspondence to:

NJMSE Managing Editor
Department of Polymer and Textile Engineering
Ahmadu Bello University
Zaria, Nigeria.
; +2348034718487; +2348025672474
njmsemanagingeditor@msn.ng.

Dr. (Engr.) Adekunle Oyelami,
Department of Mechatronics Engineering,
Federal University of Agriculture,
Abeokuta, Ogun State, Nigeria.
+2348033678832;
njmse@msn.ng; njmse.msn@gmail.com;

<http://njmse.msn.ng/>
editorinchief@msn.ng; njmse.editor.in.chief@gmail.com;

TABLE OF CONTENT

Page No

Bulus Habila, Tashi Umar Tijjani, Saidu Simon Moses, Uwanta Emaime Jimmy, Gaiya Jonathan Danladi, Shekarri Ninnas Tachye, Muazu Balarabe Babangida, Ahmed Salim, Joseph Igbehinadun Olajide, Adamu Audu and TureSunday Dahiru.

Investigation into the Bating Potential of Musa Accuminata (Banana) Peel in the Production of Leather

34 - 38

Aremo Bolaji, Adeoye Mosobalaje O., Obioh Imoh B., Okuwa Charles T., Oyinseye Shola I., Isadare Dayo A., Ayodeji Sodrudeen A., Abiodun Bukunmi J. and Adeboye Odun A.

The Re-Imagination of Electrochemical Power: A Global Awak-ening and Thoughts from Obafemi Awolowo University, Ile-Ife.

39 - 51

Oyegoke Ademola, Oyegoke Toyese, and Jacob John Olusanya.

Computational Study of CO Adsorption Potential of MgO, SiO₂, Al₂O₃, and Y₂O₃ Using a Semiempirical Quantum Calculation Method

52 - 57

Omotajo Adewole Adeyemi; Omotola Tobilola Emmanuel; Olawale, John O.; Isadare Dayo A.; Adetunji Adelana R.; Adekoya O. and Adeyemo, O.

Characterization of Some Selected Silica Sand Deposits in South West Nigeria for Sand Moulding in Foundry Industry

58 - 69

Dodo Rayyan M., Abubakar Ibrahim I., Bello Kamilu A., Asuke Ferdinard, Abdullahi Ibrahim and Shamsu Mohammed

Evaluation of Abrasion, Biocompatibility and Degradation Behavior of Polypropylene/ Sugarcane Bagasse Ash Particulate Composites for Dental Application

70 - 74

Shittu Moshood Dehinde, Owolabi Babatunde Michael, Ibitoye Simeon Ademola and Olawale John Oluyemi

Effects of Ingate types on Some Mechanical Properties of Cast Aluminium 6063 Alloy

75 - 78

Kuye Sidikat I., Oladerin Kolawole O., Adetunji Olayide R. and Makinde Victor O.

Mechanical And Microstructural Properties Of Al-Sic Auto Brake Disc Rotor Composite

79 - 85

Oladejo Oluseyi O.

Development of a Computational Model for Monitoring Pipeline Network Using Unmanned Aerial Vehicle

86 - 90

Abdulrahman Musa, Hamza Abba and Muhammad Abubakar Lawal

Study on the Thermal Properties of Epoxy Resin Reinforced with Arylidene-based Polybenzoxazine

91 - 98

Ibrahim Abdulkadir, Bice S. Martincigh and Sreekantha B. Jonnalagadda

Synthesis, Characterization, Magnetic and Photocatalytic properties of Bi, Co and Mn Co-doped Neodymium Ferrite (Nd_{0.5}Bi_{0.2}(Co_{0.2}Mn_{0.1})FeO_{3-δ}) Solid Solution

99 - 106

Adeyemi S. S., Sogbesan A. O., Adetunji, A. Rasak, Isadare Dayo A., Olawale John Oluyemi, Adekoya O. and Adeyemo O.

Determination of the Suitability of Locally Available Aluminum Scrap for Production of Motorcycle Brake Shoe

107-116

Ofem Michael Ikpi, Ubi Paschal Ateb, Christian Christian Adi and Ekpe Ubong Pius.

Mechanical Modelling of Bamboo Sawdust/polyester Composites Fabricated by Hot Pressing Method

117-124

Mechanical Modelling of Bamboo Sawdust/polyester Composites Fabricated by Hot Pressing Method

*Ofem Michael Ikpi, ¹Ubi Paschal Ateb, ²Christian Christian Adi and ³Ekpe Ubong Pius

Department of Mechanical Engineering, Cross River University of Technology, Calabar, Nigeria

¹Department of Mechanical Engineering, University of Calabar, Calabar, Nigeria

²Department of Mechanical Engineering, Federal University Otuoke, Bayelsa State Nigeria

³Department of Mechanical Engineering, Akwa Ibom State college of Science and Technology Nung Ukim Ikono LGA

*Corresponding E-mail: michaeliofem@crutech.edu.ng.

Abstract

Bamboo fibres of 1 to 3 mm sizes were milled to particle size of approximately 100µm using a hammer mill. The bamboo sawdust (BS) was chemical treated using NaOH of concentration 6 % wt/v for 72 h at room temperature. Dried bamboo sawdust was mixed with polyester at different weight ranging from 0 % to 24 % wt. %. The composites were tested for the tensile properties. Theoretical mechanical equations were used to predict the properties. Polyester curve showed linear deformation behaviour with the stress rising to a maximum value with signs of yielding before fracture. The tensile strength of polyester was 49.38 MPa, increasing to a maximum of 76.47 MPa at 24 % wt. of BS. At zero wt. % of BS the modulus was 1381 MPa, and increased to 2587.08 MPa at 24 % wt. The strain decreased from 5.5 % at pure polyester to 3.32 % at 24 % wt. of BS. A maximum percentage decrease of ≈ 40 % for the strain was recorded, an indication of the brittleness of the composites. Prediction of mechanical properties using published theories of mechanical equations (tensile strength and Young's modulus) with experimental results of bamboo sawdust reinforced polyester composites was investigated. The models used were rule of mixture (Parallel and Series), Hirsch's and Halpin-Tsai models. Irrespective of the equation used tensile strength increased with increase in the volume fraction of BS. The best correlation between theoretical and experimental tensile strength was predicted using the Halpin-Tsai model, followed by Hirsch, Parallel and Series respectively. Depending on the volume or weight fraction the percentage prediction was between 79 and 88 % for Parallel and Series models and between 97 and 99 % for Halpin-Tsai and Hirsch models.

Keywords: strength, modulus, mechanical theories, modelling.

1. INTRODUCTION

A composite is a material comprising of a mixture of two or more (insoluble in each other) constituents, which differ in chemical and form composition. One major advantage of composites material is the high specific strength and stiffness compared to the individual components. A composite can be produced from a mixture of a polymer matrix and a synthetic fibre acting as a reinforcing material (Bledzki and Gassan, 1999). Aramid, glass and carbon fibres are often used as reinforcement for polymer composites. The major reason for the wide usage is their strength and availability. The applications of these fibre reinforced composites cut across building materials, civil engineering, boat hulls, automobile and aerospace industries (Manalo *et al.*, 2015; Huang and Young, 2019). Besides, demanding energy (Zhang *et al.*, 2018), involved in the usage of synthetic fibres, has brought about environmental concern due to the none-biodegradability (Huang and Young, 2019). The aforementioned problems on synthetic fibre can be fixed by using the natural fibres as reinforcement for polymer composite fabrication (Faruk *et al.*, 2014)

Natural fibre can be considered as an alternative to synthetic fibre reasons been due to their high strength, low cost, lightweight, biodegradability, renewability, low cost, low energy requirements, ease of separation, abundant and local availability (Li *et al.*, 2007). Examples of natural fibres that have attracted research include sisal, kenaf, jute, coir flax, and bamboo fibre (Baley *et al.*, 2018; Prasob and Sasikumar, 2019; Koronis *et al.*, 2017; Sen and Reddy 2011; Saba *et al.*, 2015). Natural fibres can be grouped according to their origin; these are animals, plants, or minerals. Fibres from animal can be found in sea shells example is crab (Ofem, 2018). Plant fibres, can be subdivided into non-wood fibres (leaf, seed-hair and bast fibres) and wood fibres (softwood and hardwood fibres). The major constituents of vegetable fibres are lignin, cellulose, and matrix polysaccharides (Akil *et al.*, 2011)

Bamboo is one of the fast growing, low-cost and locally available natural materials in most developing countries. Bamboo being a natural hierarchical cellular material can give good mechanical properties, along its fibre direction (Wegst and Ashby, 2004). Among nu-

merous natural fibres, bamboo fibre has drawn specific consideration due to its low-density, high stiffness, high strength and rapid growth (Okubo *et al.*, 2009; Osorio *et al.*, 2011). Several treatments of bamboo culm are needed to obtain bamboo fibre. Extraction methods needed to obtain bamboo fibre from bamboo culm include retting, alkali treatment, crushing, grinding, milling and degumming (Zakikhani *et al.*, 2014; Rao and Rao 2007; Biswas *et al.*, 2013). The extraction method can affect the quality and strength of the fibres.

Alkali treatment of bamboo fibre has being the most commonly used and comparatively economical chemical treatment (Izani *et al.*, 2013; Senthilkumar, *et al.*, 2019). The essence of the chemical treatment is to effectively modify the fibre surface to boost the interfacial adhesion between the fibre and the polymeric matrix (Reddy *et al.*, 2013). Other chemicals used for modification of fibre surfaces are maleic anhydride-grafted (Chen *et al.* 1998) sodium hydroxide (Huang and Young, 2019; Izani *et al.*, 2013; Senthilkumar *et al.*, 2019; Khan *et al.*, 2017), Sodium hypochlorite (NaClO) (Li *et al.*, 2007), and benzoate (Chen *et al.*, 2018). Huang and Young (Huang and Young, 2019) reported the mechanical, hygral, and interfacial strength of continuous bamboo fibre reinforced epoxy. Sodium hydroxide (0.1 N of NaOH at 100°C for 12 h) was used to modify the surface area of the fibre. At 42 % volume fraction alkali treatment improved the adhesion between epoxy polymer and bamboo fibre.

The effect of maleic anhydride-grafted polypropylene (MAPP) on the mechanical properties of bamboo fibre-reinforced composite has been reported (Chen *et al.*, 1998). At 24 wt. % of MAPP, while the tensile strength of the composite was 32–36 MPa, tensile modulus was 5–6 GPa. It was observed that the composite is lighter, water-resistant, cheaper, and has a tensile strength three times higher than the commercially available wood pulp board. The effect of sodium silicate modification on moso-bamboo particles reinforced PVC has been reported (Wang *et al.*, 2010). Sodium silicate aqueous solutions were varied (0.5%, 1%, 2%, 5% and 10%). The result showed that the tensile strength and modulus of elasticity of the bamboo particles reinforced PVC composites increased to 15.72 MPa and 2956.80 MPa respectively at 5% concentration of sodium silicate solution.

Therefore, this work is to investigate the effect of loading on the mechanical properties of polyester resin reinforced bamboo sawdust. Four model equations will be used to predict the tensile strength and elastic modulus of the composite. To best of our knowledge the mechanical properties of bamboo sawdust reinforced polyester have not been reported. Modelling of the me-

chanical properties of bamboo fibre using established equations is limited in literature. Due to the strength of epoxy, most authors have reported the properties of bamboo fibre/epoxy composites. In this research, bamboo sawdust will be obtained from bamboo fibre after milling and chemical treatment using an alkali. Modelling of the tensile strength and modulus will be evaluated. Scanning electron microscopy (SEM) will also be used to characterize the composites.

2.0 THEORETICAL MODELLING OF MECHANICAL PROPERTIES

There is wide-ranging literature dedicated to the modelling of mechanical properties of polymers reinforced natural or synthetic fibres. The modelling is exceedingly significant and sheds light on the relationship between the composite structure and the properties of the composite. The mechanical properties (tensile and elastic) of polymer reinforced composites can be experimentally determined from a variety of mathematical models. Properties such as Poisson's ratio, elastic modulus, shear modulus, tensile strength, and relative volume fractions of both matrix and fibre are the important input properties needed to predict the mechanical properties of the composite. In some models, aspect ratio and orientation of fibre play a significant role. Many theoretical models have been reported to model the tensile strength and Young's modulus of composites. These include Rule of mixture (Parallel or Series) model, Halpin-Tsai equation, modified Halpin-Tsai equation, Hirsch's model, Einstein and Guth equations, Cox Model and Guth's Equation, Nicolais-Narkis theory and modified Bowyer and Bader's model. In this research, we will limit ourselves to Rule of mixture (Parallel or Series) model, Halpin-Tsai equation, modified Halpin-Tsai equation, and Hirsch's model equations (Facca *et al.*, 2006; Facca *et al.*, 2007; Kalaprasad *et al.*, 1997; Fornes *et al.*, 2003; Shindea *et al.*, 2017).

2.1 Rule of Mixtures Model (Parallel and Series model)

The Rule of mixtures model comprises of the parallel and the series models. They are the simplest models used to predict the elastic and tensile properties of composite materials. The applications got across both particulate and fibrous reinforcement. The parallel and series equations give the maximum and minimum possible values for E_c and T_c . The parallel model assumes iso-strain conditions for both matrix and fibre while series models assume uniform stress in both matrix and fibre. Equations 1, 2, 3 and 4 are the Rule of mixture for modulus and tensile strength (Facca *et al.*, 2006; Facca *et al.*, 2007; Kalaprasad *et al.*, 1997). The role of mixture assumes that the aspect ratio ξ approaches infinity or zero, respectively.

Parallel model

$$E_c = E_f V_f + E_p V_p \quad (1)$$

$$T_c = T_f V_f + T_p V_p \quad (2)$$

Series model

$$E_c = \frac{E_m E_f}{E_m V_f + E_f V_m} \quad (3)$$

$$T_c = \frac{T_m T_f}{T_m V_f + T_f V_m} \quad (4)$$

E_m , E_c and E_f are the elastic moduli of matrix, composite and filler, respectively. V_f and V_p are the volume fractions of filler and polymer. T_c , T_f and T_p , are the Tensile strength of composite, filler and polymer matrix, respectively.

2.2 Halpin-Tsai (H-T) Model

A semi-empirical equation to predict the elastic properties of short fibres reinforced polymer matrix was developed by Halpin and Tsai (Fornes *et al.*, 2003). The H-T models' assumed that the particle is isolated, the matrix is isotropic, viscosity is constant, filler well dispersed, has uniform shape and dimension, and is firmly adhered to the matrix. The volume fraction of the filler and its orientation are accounted by using the aspect ratio, $\xi=2l/D$ where l is the length of the fibre and D the diameter or thickness of the fibre depending on the shape. The Halpin and Tsai equations are given in Equations 5-8.

$$E_c = E_m \left\{ \frac{1 + \xi \eta V_f}{1 - \eta V_f} \right\} \quad (5)$$

$$T_c = T_m \left\{ \frac{1 + \xi \eta V_f}{1 - \eta V_f} \right\} \quad (6)$$

$$\eta = \frac{E_f / E_m - 1}{E_f / E_m - \xi} \quad (7)$$

$$\eta = \frac{T_f / T_m - 1}{T_f / T_m - \xi} \quad (8)$$

where

E_c = composites' modulus

E_m = the matrix modulus

T_c = composites' Strength

T_m = the matrix Strength

ξ = the shape factor which relates to the filler aspect ratio

V_f = the volume fraction of the filler

2.3 Hirsch's Model

Hirsch's model is a combination of series and parallel models. Hirsch's model is applicable for particulate and fibrous reinforcements. The Young's modulus and tensile strength can be calculated using the following equations (Kalaprasad *et al.*, 1997; Shindea *et al.*, 2017)

Series model

$$E_c = \chi(E_f V_f + E_p) + (1 - \chi)$$

$$V_p \frac{E_m E_f}{E_m V_f + E_f V_m} \quad (9)$$

$$T_c = \chi(T_f V_f + T_p) + (1 - \chi)$$

$$V_p \frac{T_m T_f}{T_m V_f + T_f V_m} \quad (10)$$

χ is the stress transfer parameter. χ is 0.1 for randomly oriented fibres composite.

3.0 MATERIALS AND METHODS

The following are the major materials used; bamboo chips were locally source (Ugep, Nigeria), Sodium Hydroxide (NaOH), and unsaturated polyester resin (35% solution at 20°C, M_w 600,000), Cobalt naphthanate as accelerator and methyl ethyl ketone peroxide (MEKP) from Sigma-Aldrich is used as catalyst. Bamboo fibres were cut into different sizes of between 1 to 3 mm washed in water to remove impurities like sand, debris etc. Washed fibres were dried in sun until the weight of fibre was constant. Chemical treatment of the bamboo fibre was performed using NaOH of concentration 6% wt./v for 72 hrs at room temperature. After 72 hrs the bamboo fibres were removed and soaked in distilled water to reduce the brittleness and also dilute the alkaline content. Washing of the fibre is done in running water until the pH of the fibre is neutral. Sawdust of bamboo was prepared by crushing the fibres to particle size of approximately 100 μm using a hammer mill. The bamboo sawdust was dried in an oven at a temperature of 60°C for 24 hrs or until the weight is constant. Treated bamboo sawdust was mixed with polyester (after mixing with accelerator and catalyst at room temperature for curing at 1% by volume of resin) at different weight ranging from 0 to 24% wt. of bamboo. The mixing was done by dispersion and hot pressed using 120 ton hydraulic hot press to make samples for tensile testing. The composite specimens were cured for 24 hrs and post cured for another 3 hrs at 60°C

3.1 Characterisations of Composite

Mechanical properties were evaluated using Instron Universal Testing Machine (Instron 1121), fitted with a 20KN load Cell. The tensile test was performed at a crosshead speed of 2 mm/min. Films were conditioned in desiccators under 50% RH, at 25°C, for 48 h before being characterized for mechanical properties. A micrometre screw gauge was used to measure the thickness. Measurements were taken from three different positions and an average value was used. Between 3 and 5 specimens were tested for each % weight. The mechanical properties were measured according to ASTM D882-02 (2002). The fracture surface of BS-P composites was examined by scanning electron microscopy (SEM) to investigate the failure mechanism of fracture. An EVO 60 scanning electron microscope was used to study fracture surfaces. Using a low-vacuum sputtering machine, samples were coated with gold mounted on a silver-paint holder before inserted into the SEM chamber. SEM imaging was employed using an accelerating voltage of 5 kV. To prepare specimens for SEM, fracture surfaces were first flushed with distilled water to remove any debris. Table 1 is the nomenclature of bamboo sawdust/polyester resin.

Table 1: Nomenclature of BS/P blended specimen

Abbreviations	Full name
P	Neat Polyester film
BS	Bamboo Sawdust
BS/P10	Polyester blend (10 wt.% bamboo sawdust)
BS/P12	Polyester blend (12 wt.% bamboo sawdust)
BS/P14	Polyester blend (14 wt.% bamboo sawdust)
BS/P16	Polyester blend (16 wt.% bamboo sawdust)
BS/P18	Polyester blend (18 wt.% bamboo sawdust)
BS/P20	Polyester blend (20 wt.% bamboo sawdust)
BS/P22	Polyester blend (22 wt.% bamboo sawdust)
BS/P24	Polyester blend (24 wt.% bamboo sawdust)

4.0 RESULTS AND DISCUSSION

4.1 Tensile Behaviour

Results of mechanical properties were compared using ANOVA multiple comparison tests ($p < 0.05$). Tensile properties were measured according to ASTM D882-02 (2002) standard. Figure 1 is the stress-strain curves of polyester and bamboo fibre. Alkali or acid hydrolysis is used in chemical processing to remove the amorphous regions of raw cellulose fibre. It is worth noting that the alkali solution influences not only the cellulosic components inside the plant fibre, but also the noncellulosic components (hemicellulose, lignin, and pectin). A typical stress-strain plot for the resin and bamboo fibre is shown in Figure 1. Polyester curve shows linear deformation behaviour with the stress rising to a maximum value which shows sign of yielding (σ_y) before fracture occurred (σ_f). The Young's modulus, E , of the poly-

ter resin was calculated from the slope of the curve. Fracture toughness is a measure of a material's resistance to crack propagation, but in a composite this can be hard to measure accurately. However, the stress strain curve of the resin system on its own provides some indication of the material's toughness. Generally the more deformation the resin will accept before failure the tougher and more crack-resistance the resin will be. The bamboo fibre has a significantly higher tensile strength with, a significantly lower failure strain.

Various authors have reported divergent properties of bamboo reinforced composites. The differences in properties are attributed to the method of preparation, growth, source and method extraction, percentage

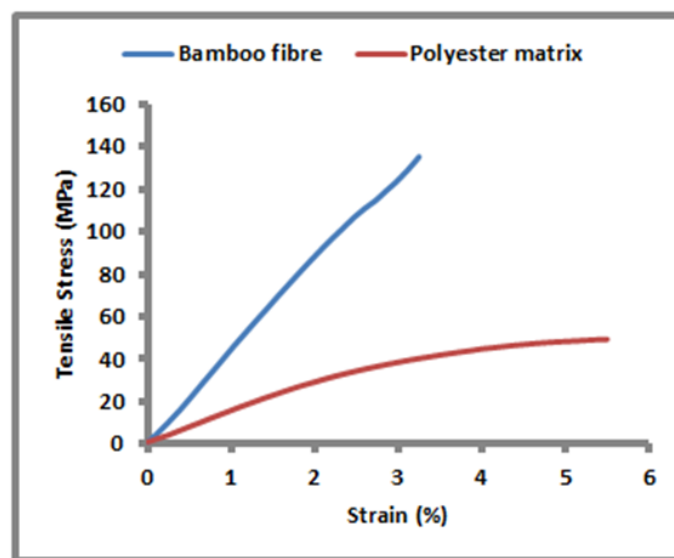


Figure 1: Stress-strain curves of polyester and bamboo

Figure 2 is the stress-strain curves of polyester reinforced bamboo composites. The tensile strength of pure polyester is 49.38 ± 2.34 MPa, and this value increases to a maximum of 76.47 ± 5.23 MPa at 24 % wt. of polyester. The same pattern of increment for Young modulus was observed. At zero wt. % of polyester the modulus is 1381.2 ± 134.21 MPa, it increases to 2587.08 ± 148.22 MPa at 24 % wt. For the strain, it decreases from 5.50 ± 0.15 % at pure polyester to 3.32 ± 0.72 % at 24 % wt. It should be noted that the maximum percentage decrease of the strain is ≈ 40 % an indication of the brittleness of the composites. The increase in tensile strength with increase in filler contents may be attributed to the likely homogeneous dispersion of bamboo sawdust within the polyester matrix and the resulting compatibility. The compatibility is possible due to a large number of hydroxyl groups in their structures. Due to the compatibility structural defects within the composite is maintained at minimum even at higher loading leading to better mechanical performance (Ni *et al.*, 2006).


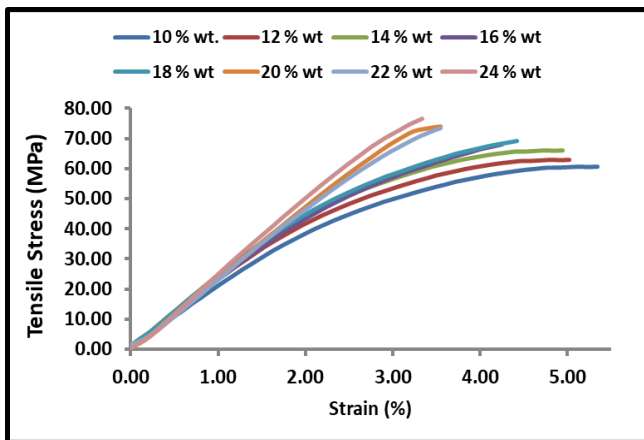



Figure 2: Stress-strain curves of polyester reinforced bamboo composite

weight of bamboo, chemical modification or treatment of bamboo, time is taken to process the blend, type and amount of plasticizer used (Zhang *et al.*, 2018; Osorio, *et al.*, 2011). Zhang *et al.*, (2018), reported an increase in Young modulus, tensile strength and elongation at break and with an increase in wt. % of NaOH when 30 wt. % of epoxy reinforced bamboo fibre were fabricated. Tensile strength increases from 262 MPa of untreated bamboo to 362 MPa at 6 wt. % of NaOH. The same pattern was observed for Young modulus. While the strain continued to increase beyond 6 wt. % of NaOH, tensile strength and modulus dropped to 235 MPa and 6.1 GPa (from 9.8 GPa for untreated bamboo) respectively.


It was reported that at 2 wt.% NaOH treatment only a small part of the surface substances could be removed, an indication that large quantity of sticky materials still can still be found, acting as constraint among cellulose chains. This constraint would check the fibrils from repositioning themselves in a dense manner along the direction of force during the tensile testing. At 6 wt. % NaOH treatment, 38% and 14%, increment was recorded, the constrain at 2 wt. % NaOH treatment must have been removed. In this research 6 wt. % NaOH treatment was carried out. The gradual increase of mechanical properties even at 24 wt. % of bamboo sawdust is an indication that all sticky materials which could have acted as constrain have been removed at 6 wt. % NaOH treatment. In addition agglomeration at this wt. % does not exist. According to Bledzki and Gassan (1999); and Sydenstricker *et al.*, (2003) removal of lignin and hemicellulose in bamboo fibres can be achieved by moderate treatment with alkali. The removal of hemicellulose and lignin will lead to increase in cellulose crystallinity invariably improved both fibre tensile strength and modulus.

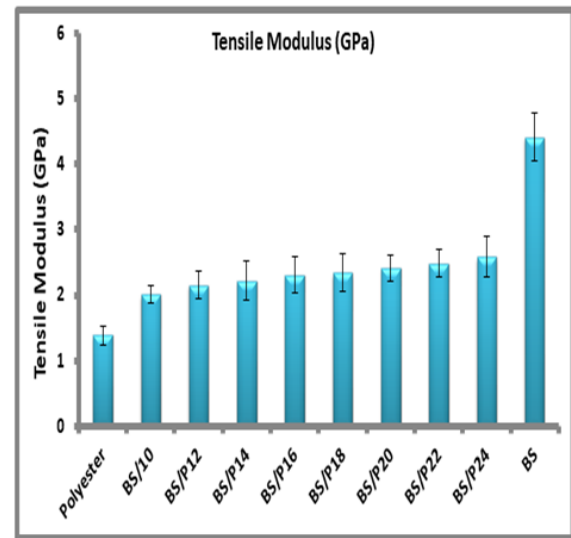

(a)

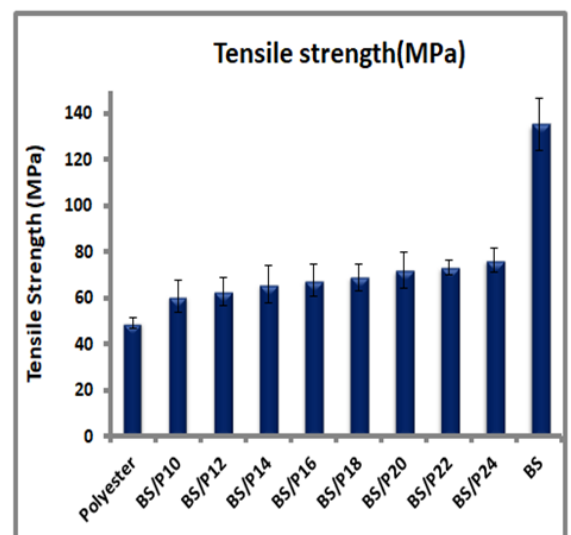

(b)

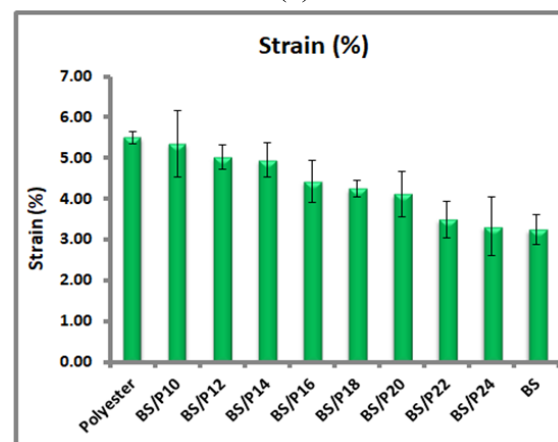

(c)

Figure 3: (a) Tensile Strength, (b) Tensile Modulus and (c) Tensile Strain of bamboo fibre reinforced Polyester matrix at different fibre weight fraction .

4.2 Modelling of Mechanical properties.

Tables 2 and 3 are the properties of Polyester and bamboo fibre needed for the modelling of the mechanical properties of Polyester reinforced bamboo sawdust. Figure 4 shows a comparison of differences in theoretical and experimental tensile strengths of Polyester reinforced bamboo sawdust composites. Theoretical values were calculated using rule of mixture (Parallel and Series), Halpin-Tsai, and Hirsch, models. In all cases, tensile strength increases with increase in the volume fraction of bamboo. The best correlation between theoretical and experimental tensile strength is predicted using the Halpin-Tsai model, followed by Hirsch, Parallel and Series respectively. Depending on the volume or weight fraction the percentage prediction is between 79 and 88 % for Parallel and Series models and between 97 and 99 % for Halpin-Tsai and Hirsch models. Parallel and Series models may be used to describe the strength of both particulate and fibrous reinforced composites (Facca *et al.*, 2007) and give the maximum and minimum values respectively for both tensile strength and Young modulus of the composites. While Series model assumes uniform stress, Parallel model assume uniform strain. The stress transfer mechanism for particulate or short reinforced composites is different from that of the continuous fibre composites. For a short fibre composite the stress transfer depends on the stress concentration at the ends of the fibre, type and amount of plasticizer, critical length fibre, method of preparation of films, modification of fibre and orientation of fibre, among others. From Figure 4 irrespective of the volume fraction H-T model agrees between 97.62 (24% weight of bamboo sawdust), and 99.28% (10% weight of bamboo sawdust), with the experimental values. For Parallel model is between 82% (24 % weight of bamboo sawdust) and 88.53% (10% weight of bamboo sawdust). The high percentage agreement with experimental values is an indication that uniform strain or stress has been achieved in the composite. Hirsch model is an equation that combined the Series and Parallel models, with the insertion of a parameter χ . Like Series and Parallel models, Hirsch model is compatible with particulate and fibrous reinforcements. The theoretical and experimental values can have between 98.13% and 99.98 % irrespective of the volume fraction when the value of χ in Equation 10 is 0.55. Bearing in mind the assumption made for Series and Parallel models which are applicable here, it will be right to conclude that at $\chi = 0.55$ uniform stress and strain have been achieved, that is χ is a parameter which defines the level of stress transfer between matrix and fibre. For a short fibre, the governing indices for the value of χ are fibre

orientation, fibre length and stress concentration at the ends of fibre (Kim *et al.*, 2003).

Figure 5 shows a comparison of the difference in theoretical and experimental elastic modulus of bamboo sawdust reinforced polyester composites. From the figure Series model could give a correlation between theoretical and experimental values up to 75 % at 10% weight fraction. Contrary to the tensile modelling, Halpin-Tsai model could give up to 87.5 % at 10% weight fraction and 86.59% at 24% weight fraction. Both Hirsch and Parallel, could predict between 95.18 and 99.61%. For Hirsch model this percentage can only be achieved when the value of χ in Equation 9 is 0.99. The constraint of the models used here mainly depends on different factors among which are micro-voids be-

Table 2: Physical and mechanical properties of polyester

Density (g/cm ³)	Tensile strength at break (MPa)	Elongation at break (%)	Modulus of elasticity (MPa)
1.2	49.38	5.50	1381.2

Table 3: Mechanical properties of bamboo fibre

Density (g/cm ³)	Tensile strength at break (MPa)	Elongation at break (%)	Modulus of elasticity (MPa)	Aspect ratio
0.7	135.3	3.25	4324.82	1.4

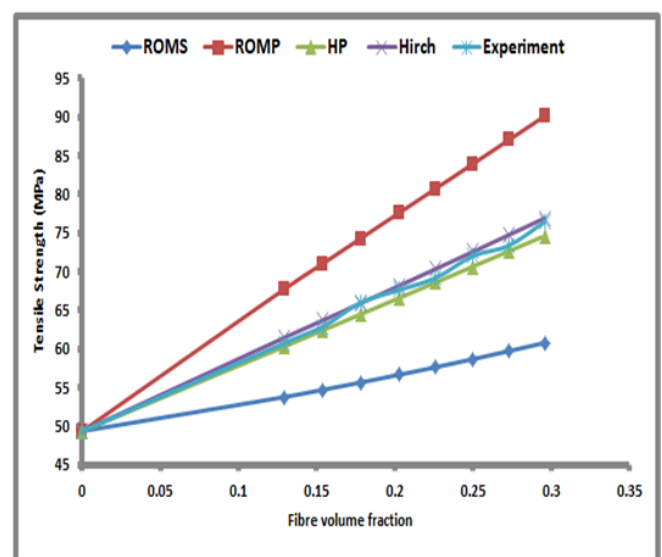


Figure 4: Tensile strength of Bamboo/Polyester composite modelled by Parallel, Series, Halpin-Tsai, and Hirsch

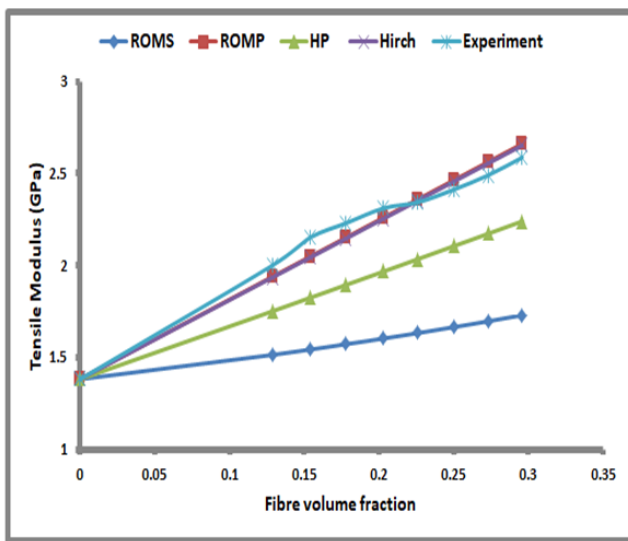


Figure 5: Elastic modulus of Bamboo/Polyester composite modelled by Parallel, Series, Halpin-Tsai, and Hirsch

tween fibre and matrix during composites formation; this factor is not taken care of in the cause of the model formulation.

5.1 Morphology

The SEM images of fractured polyester, bamboo fibre and bamboo sawdust/polyester composites are shown in Figure 6. A - F. Figure 6A shows the SEM images of fractured surface of neat polyester. The surface is relatively smooth but appeared ductile. In the absence of fibre in the matrix the crack growth will transmit in an unstable manner upon application of external loading. A matrix plastic deformation can be observed at the crack tip of the matrix. No significant fibre pull-out was observed in the entire composites irrespective of the filler loading. Fibre pull-out will be depicted by extruding fibres and holes. The low fibre pull-out could be attributed to smaller particles (approximately 100 μm) of fibres in the form of sawdust. Another reason could be attributed to good fibre dispersion within the matrix. Fibre pull-out is unfavourable to the strength and modulus of composites. However, it provides a major energy dissipation source during material failure (Jiang *et al.*, 2010). In terms of viscosity, polyester matrix was capable of entering the flaws in bamboo sawdust there by eliminating voids between fibre sawdust. This will result into better load transfer between the fibres and the matrix and subsequently better mechanical properties even at higher loading in other words there is an effective stress transfer between matrix and fibre sawdust. The gradual increase in tensile stress and modulus at higher loading is an indication that the flow rate of resin to infiltrate the voids between the fibres is not reduced.

4.0 CONCLUSION

A comparison between experimental results and the prediction from theories of mechanical properties (tensile strength, elongation at break, and Young's modulus) of bamboo fibre sawdust reinforced Polyester composites has been presented. The models used were Parallel and series model of rule of mixture, Hirsch's model, and Halpin-Tsai model. Properties of bamboo sawdust composites were presented as a function of volume fraction of the resin. All models were applied in tensile strength and Young modulus.

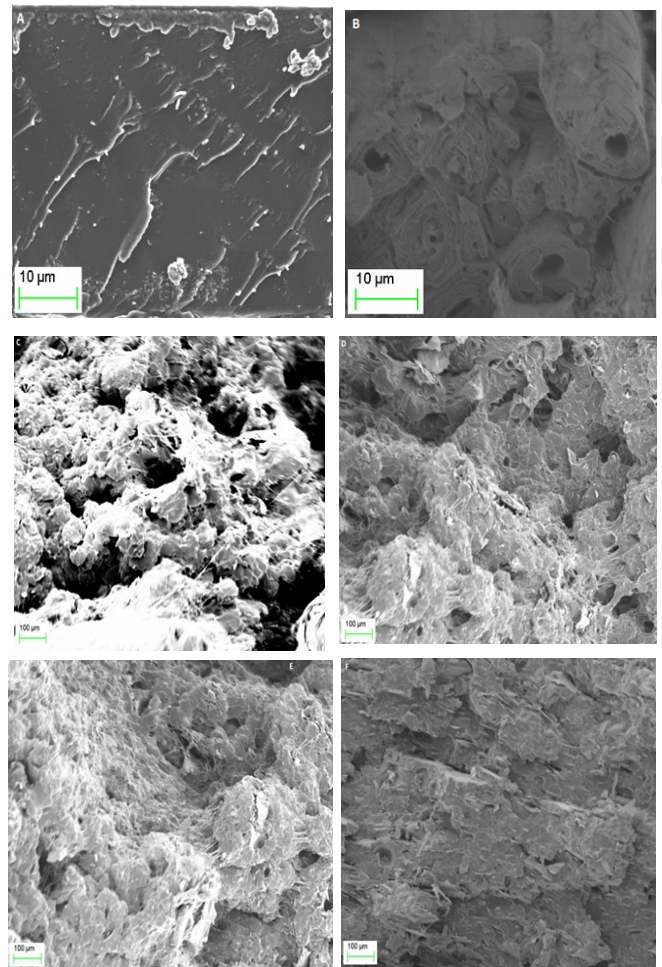


Figure 6: SEM images of polyester, bamboo, and bamboo sawdust/polyester composite after fracture (A) Polyester, (B) Bamboo fibre, (C) 10 %wt., (D) 14 % wt., (E) 18% wt., and (F) 22% wt.

The tensile strength of polyester increases from 49.38 MPa, to a maximum of 76.47 MPa at 24 % wt. of BS. At zero wt. % of BS the modulus of polyester is 1.38 GPa, this value increases to 2.59 GPa at 24 % wt. The strain decreases from 5.5 % at pure polyester to 3.32 % at 24 % wt. of BS an indication of increase in brittle of composite. Irrespective of the theory equation used, tensile strength increases with increase in the volume fraction of BS. The best correlation between theoretical and experimental tensile strength is predicted using the Halpin-Tsai model, followed by Hirsch, Parallel and Series respectively. Depending on the volume or weight fraction the percentage prediction is between 79 and 88 % for Parallel and Series models and between 97 and 99 % for Halpin-Tsai and Hirsch models. Halpin-Tsai model could predict up to 87.5 % of modulus at 10% weight fraction and 86.59% at 24% weight fraction. Both Hirsch and Parallel, could predict between 95.18 and 99.61% of the modulus. For Hirsch model this percentage can only be achieved when the value of χ in equations is 0.99.

REFERENCE

- Akil, H., Omar, M., Mazuki, A., Safiee, S., Ishak, Z., and AbuBakar, A. (2011). Kenaf fibre reinforced composite; A review. *Materials and Design*, 32:4107-4121.
- Baley, C., Lan, M., Bourmaud, A., and Duigou, A. Le. (2018). Compressive and tensile behaviour of unidirectional composites reinforced by natural fibres: influence of fibres (flax and jute), matrix and fibre volume fraction. *Material Today Communication* 16:300-306.
- Bledzki, A. and Gassan, J. (1999). Composites reinforced with cellulose based fibres. *Progress in Polymer Science*, 24:221-274.
- Biswas, S., Ahsan, Q., Cenna, A., Hasan, M. and Hassan, A. (2013). Physical and mechanical properties of jute, bamboo and coir natural Fibre. *Fibers Polymer*, 14:1762-1767.
- Chen, X., Guo, Q. and Mi. Y. (1998). Bamboo Fiber-Reinforced Polypropylene Composites: A Study of the Mechanical Properties. *Journal of Applied Polymer Science*, 69:189-1899.
- Chen, H., Zhang, W., Wang, X., Wang, H., Wu, Y., Zhong, T. and Fei B. (2018). Effect of alkali treatment on wettability and thermal stability of individual bamboo fibers. *Journal of Wood Science*, -405.
- Facca, A. G., Kortschot, M. T. and Yan, N. (2006). Predicting the elastic modulus of natural fiber reinforced thermoplastics. *Composite Part A: Applied Science and Manufacturing*, 37:1660-1671.
- Facca, A. G., Kortschot, M. T. and Yan, N. (2007). Predicting the tensile strength of natural fiber reinforced thermoplastics. *Journal of Composites Science and Technology*, 67:2454-2466.
- Faruk, O., Bledzki, A. K., Fink, H. and Sain, M. (2014). Progress report on natural Fiber reinforced composites. *Macromolecular Materials and Engineering*, 299:9-26.
- Fornes, T. and Paul, D. (2003). Modelling properties of nylon 6/clay nanocomposites using composite theories. *Polymer*, 44:4993-5013.
- Huang, J. and Young, W. (2019). The mechanical, hygral, and interfacial strength of continuous bamboo fiber reinforced epoxy composites. *Composite Part B: Engineering*, 166:272-283.
- Izani, N., Tahir, P. M., Khairun, M. and Uyup, A. (2013). Effects of fiber treatment on morphology, tensile and thermogravimetric analysis of oil palm empty fruit bunches fibers, *Composite Part B Engineering* 45(1): 1251-1257.
- Jiang, L., Chen, F., Qian, J., Huang, J., Wolcott, M., Liu, L. and Zhang, J., (2010). Reinforcing and Toughening Effects of Bamboo Pulp Fiber on Poly(3-hydroxybutyrate-co-3-hydroxyvalerate) Fiber Composites. *Industrial & Engineering Chemistry Research* 49:572-577.
- Kalaprasad, G., Joseph, K., Thomas, S. and Pavithran, C. (1997). Theoretical modelling of tensile properties of short sisal fiber-reinforced low-density polyethylene composites. *Journal of Materials Science*, 32:4261-4267.
- Khan, Z., Yousif, B.F. and Islam, M. (2017). Fracture behaviour of bamboo fiber reinforced epoxy composites, *Composite Part B: Engineering*, 116:186-199.
- Kim, D.H., Na, S.K. and Park, J.S. (2003). Preparation and characterization of modified starch-based plastic film reinforced with short pulp fibre. II Mechanical properties. *Journal of Applied Polymer Science*, 88:2108-2117.
- Koronis, G., Silva, A. and Foong, S. (2017). Predicting the flexural performance of woven flax reinforced epoxy composites using design of experiments. *Material Today Communication* 13:317-324.
- Li, X., Tabil G. L. and Panigrahi, S. (2007). Chemical treatments of natural fiber for use in natural fiber-reinforced composites: a Review. *Journal of Polymer and Environment* 15:25-33.
- Manalo, A. C., Wani, E., Azwa, N., and Karunasena, W. (2015). Effects of alkali treatment and elevated temperature on the mechanical properties of bamboo fibre polyester composites. *Composite Part B: Engineering*, 80:73-83.
- Ni, W., Wang, B., Wang, H. and Zhang, Y. (2006). Fabrication and Properties of Carbon Nanotube and Poly(vinyl alcohol) Composites. *Journal of Macromolecular Science, Part B: Physics*, 45-659-664.
- Ofem, M. I. (2018). Deformation of micro-fibrillated chitin film and composites. *Journal of Material Science*, 53:8666-8675.
- Okubo, K., T. Fujii, T., and Thostenson, E. T. (2009). Thostenson, Multi-scale hybrid biocomposite :processing and mechanical characterization of bamboo fiber reinforced PLA with microfibrillated cellulose, *Composite Part A: Applied Science and Manufacturing*, 40:469-475.
- Osorio, L., Trujillo, E., Van-Vuure, A. W. and Verpoest, I.

- (2011). Morphological aspects and mechanical properties of single bamboo fibers and flexural characterization of bamboo/epoxy composites. *Journal of Reinforced Plastic Composite* 30:396-408.
- Prasob, P. A. and Sasikumar, M. (2019). Viscoelastic and mechanical behaviour of reduced graphene oxide and zirconium dioxide filled jute/epoxy composites at different temperature conditions. *Material Today Communication* 19:252–261.
- Rao, K. M. M. and Rao, K. M. (2007). Extraction and tensile properties of natural fibers : vakka, date and bamboo. *Composite Structures* 77-288-295.
- Reddy, K., Maheswari, C., Shukla, M., Song, J. and Rajulu, A. (2013). Tensile and structural characterization of alkali treated Borassus fruit fine fibers. *Composite Part B: Engineering*, 44:433-438.
- Saba, N., Paridah, M. T. and Jawaid, M. (2015). Mechanical properties of kenaf fibre reinforced polymer composite: A review. *Construction and Building Materials*, 76:87-96.
- Sen, T. and Reddy, H. N. J. (2011). Application of sisal, bamboo, coir and jute natural composites in structural upgradation. *International Journal of Innovation, Management and Technology* 2:186-191.
- Senthilkumar, K. Saba, N. R. N., Jawaid, M. C. M. and Siengchin, S. (2019). Effect of alkali treatment on mechanical and morphological properties of pineapple leaf fibre/ polyester composites, *Journal of Polymer and Environment*, 27:1191-120.
- Shindea, S. S., Salveb, A. V. and Kulkarnic, S. (2017). Theoretical modeling of mechanical properties of woven jute fibre reinforced polyurethane composites. *Materials Today: Proceedings*, 4:1683-1690.
- Sydenstricker, T. H., Mochnaz, S. and Amico, S. C. (2003). Pull-out and other evaluations in sisal-reinforced polyester biocomposites. *Polymer Testing*, 22:375-380.
- Wang H, Sheng K C, Chen J, Mao, H. L. and Qian X. Q. (2010). Mechanical and thermal properties of sodium silicate treated moso bamboo particles reinforced PVC composites. *Science China Technological Science*, 53 (11):2932–2935.
- Wegst, U. and Ashby, M. (2004). The mechanical efficiency of natural materials. *Philos. Magazine* 84:2167-2186.
- Zakikhani, P., Zahari, R., Sultan, M. T. H. and Majid, D. L. (2014). Extraction and preparation of bamboo fibre-reinforced composites, *Materials and Design*, 63:820-828
- Zhang, K., Wang, F., Liang, W., Wang, Z., Duan, Z. and Yang, B. (2018). Thermal and mechanical properties of bamboo Fiber reinforced epoxy composites. *Polymers (Basel)*, 10(6):608,